

# Nonlocal damage modelling for finite element simulations of ductile steel sheets under multiaxial loading

Marvin Nahrman<sup>1,\*</sup> und Anton Matzenmiller<sup>1,\*\*</sup>

<sup>1</sup> Institute of Mechanics, Dept. of Mechanical Engineering, University of Kassel, Mönchebergstr. 7, 34125 Kassel, Germany

The finite element simulation of forming processes or vehicle crash scenarios involves multiaxial loading conditions in general. Thereby, damage and failure in ductile steel sheets is triggered by void growth under hydrostatic tensile loading or by void elongation within a narrow band under shear dominated loading. These different damage mechanisms are considered by a stress state dependent continuum damage model. The damage initiation and failure are represented by a critical and a failure strain. Both are HOSFORD-COULOMB type functions of the stress triaxiality and the LODE parameter and, thus, incorporate the stress state dependence of the damage mechanisms. Due to the pathological mesh sensitivity for continuum damage models, an enhancement towards nonlocal damage evolution is carried out. Thereby, two options are investigated and compared: the integral nonlocal formulation and the gradient enhanced approach. Finally, the proposed nonlocal ductile damage model is verified for a wide range of stress states by test data of various tensile and shear specimens.

© 2021 The Authors. *Proceedings in Applied Mathematics & Mechanics* published by Wiley-VCH GmbH.

## 1 Stress state dependent nonlocal ductile damage model

The proposed constitutive equations include a plasticity model, consisting of the VON MISES yield criterion and nonlinear isotropic hardening, see [1] and [2]. The plasticity model is coupled to a continuum damage mechanics based approach by the concept of effective stresses. Thereby, isotropic damage is represented by the damage variable  $D$ . Damage growth is proposed by means of an evolution equation for the damage variable, driven by the equivalent plastic strain  $\bar{E}_{pl}$ . The damage exponent  $n_D$  controls the nonlinearity of the damage evolution behaviour. In order to consider stress state dependent damage and failure, the stress triaxiality  $T = \frac{I_1}{3\sqrt{3}J_2}$  and the LODE parameter  $\bar{L} = 1 - \frac{2}{\pi} \arccos(\frac{3\sqrt{3}}{2} \frac{J_3}{J_2^{3/2}})$  are applied for stress state characterisation, based on the first basic stress invariant  $I_1$  and the second and third deviatoric stress invariants  $J_2$  and  $J_3$ . Consequently, the damage initiation criterion  $\varepsilon_c(T, \bar{L})$  as well as the failure criterion  $\varepsilon_f(T, \bar{L})$  depend on the stress triaxiality and the LODE parameter, whereby the HOSFORD-COULOMB model from [3] is applied for both functions. Finally, the following set of equations is obtained for the stress state dependent ductile damage model:

$$\dot{D} = \frac{n_D}{\varepsilon_f(T, \bar{L}) - \varepsilon_c(T, \bar{L})} \left\langle \frac{\bar{E}_{pl} - \varepsilon_c(T, \bar{L})}{\varepsilon_f(T, \bar{L}) - \varepsilon_c(T, \bar{L})} \right\rangle^{n_D-1} \dot{\bar{E}}_{pl}, \quad \varepsilon_{c/f}(T, \bar{L}) = b_{c/f} \left( \frac{1 + c_{c/f}}{g_{c/f}(T, \bar{L})} \right)^{\frac{1}{n}} \quad (1)$$

$$g_{c/f}(T, \bar{L}) = \left[ \frac{1}{2}(f_1 - f_2)^{a_{c/f}} + \frac{1}{2}(f_2 - f_3)^{a_{c/f}} + \frac{1}{2}(f_1 - f_3)^{a_{c/f}} \right]^{\frac{1}{a_{c/f}}} + c_{c/f} (2T + f_1 + f_3) \quad (2)$$

$$f_1 = \frac{2}{3} \cos \left[ \frac{\pi}{6} (1 - \bar{L}) \right], \quad f_2 = \frac{2}{3} \cos \left[ \frac{\pi}{6} (3 + \bar{L}) \right], \quad f_3 = -\frac{2}{3} \cos \left[ \frac{\pi}{6} (1 + \bar{L}) \right] \quad (3)$$

The parameters  $a_c, b_c, c_c$  for damage initiation and  $a_f, b_f, c_f$  for failure have to be calibrated to test data, whereas the exponent is usually defined to  $n = 0.1$ .

In order to prevent the pathological mesh sensitivity for continuum damage models, an enhancement towards nonlocal damage evolution is carried out. By applying the integral nonlocal approach according to [4], the nonlocal damage  $\tilde{D}(\mathbf{x})$  at the reference point  $\mathbf{x}$  is obtained by weighting the local damage  $D(\mathbf{y})$  at neighbouring points  $\mathbf{y}$  over the integration region  $\Omega$ . Therefore, the three-parameter weighting function  $w(\mathbf{x}, \mathbf{y})$  is employed with the parameters  $p$  and  $q$  and the characteristic length  $l_{c,int}$ . Hereby,  $\|\mathbf{x} - \mathbf{y}\|$  is the EUCLIDEAN norm of the distance between  $\mathbf{x}$  and  $\mathbf{y}$ .

$$\tilde{D}(\mathbf{x}) = \frac{\int_{\Omega} D(\mathbf{y}) w(\mathbf{x}, \mathbf{y}) d\mathbf{y}}{\int_{\Omega} w(\mathbf{x}, \mathbf{y}) d\mathbf{y}}, \quad w(\mathbf{x}, \mathbf{y}) = \left[ 1 + \left( \frac{\|\mathbf{x} - \mathbf{y}\|}{l_{c,int}} \right)^p \right]^{-q} \quad (4)$$

As alternative to the integral nonlocal formulation according to Eq. (4), the implicit gradient enhanced damage approach

$$\tilde{D}(\mathbf{x}) - l_{c,grad}^2 \nabla^2 \tilde{D}(\mathbf{x}) = D(\mathbf{x}) \quad (5)$$

is applied for the nonlocal enhancement as well. The implementation into LS-DYNA® is carried out by exploiting the thermo-mechanical solver, due to the analogous field problem of the Helmholtz type inhomogeneous differential equation (5) with the steady-state heat equation.

\* Corresponding author: e-mail marvin.nahrman@uni-kassel.de, phone +49 (0)561 804 2831


\*\* Corresponding author: e-mail post-structure@uni-kassel.de, phone +49 (0)561 804 2043, fax +49 (0)561 804 2720



This is an open access article under the terms of the Creative Commons Attribution License, which permits use, distribution and reproduction in any medium, provided the original work is properly cited.

## 2 Model verification for a wide range of stress states

The model parameters are identified for the ductile steel HX340LAD on the basis of test data from the Fraunhofer Institute for Mechanics of Materials (IWM), see [6]. In order to capture a wide range of stress states, the design of experiments includes flat smooth and notched tensile specimens, various shear specimens and a NAKAZIMA biaxial punch test. The sheet thickness is 1.5 mm in all cases. The identified model parameters are already published in [1] and [2]. The simulation is carried out for the stress state dependent ductile damage model in combination with the integral nonlocal formulation denoted as (sim. int.) and the gradient enhanced damage approach with (sim. grad.) in Fig. 1 a) and b). The predicted stress-strain curves are compared to the test data in Fig. 1 a) for the tensile specimens and in b) for the shear specimens. A good overall accordance is achieved, verifying the proposed model for a wide range of stress states. Note that the numerical results, obtained by both different nonlocal methods, are nearly identical. However, a significant difference is found for the elapsed simulation time. Thereby, three different mesh sizes are evaluated for the smooth tension specimen in Fig. 1 c) and for the 0° shear specimen in d). Compared to the simulation with the gradient enhanced approach, the elapsed simulation time for the integral nonlocal formulation is noticeably higher, in particular for the very fine mesh, due to its the underlying costly search algorithm.

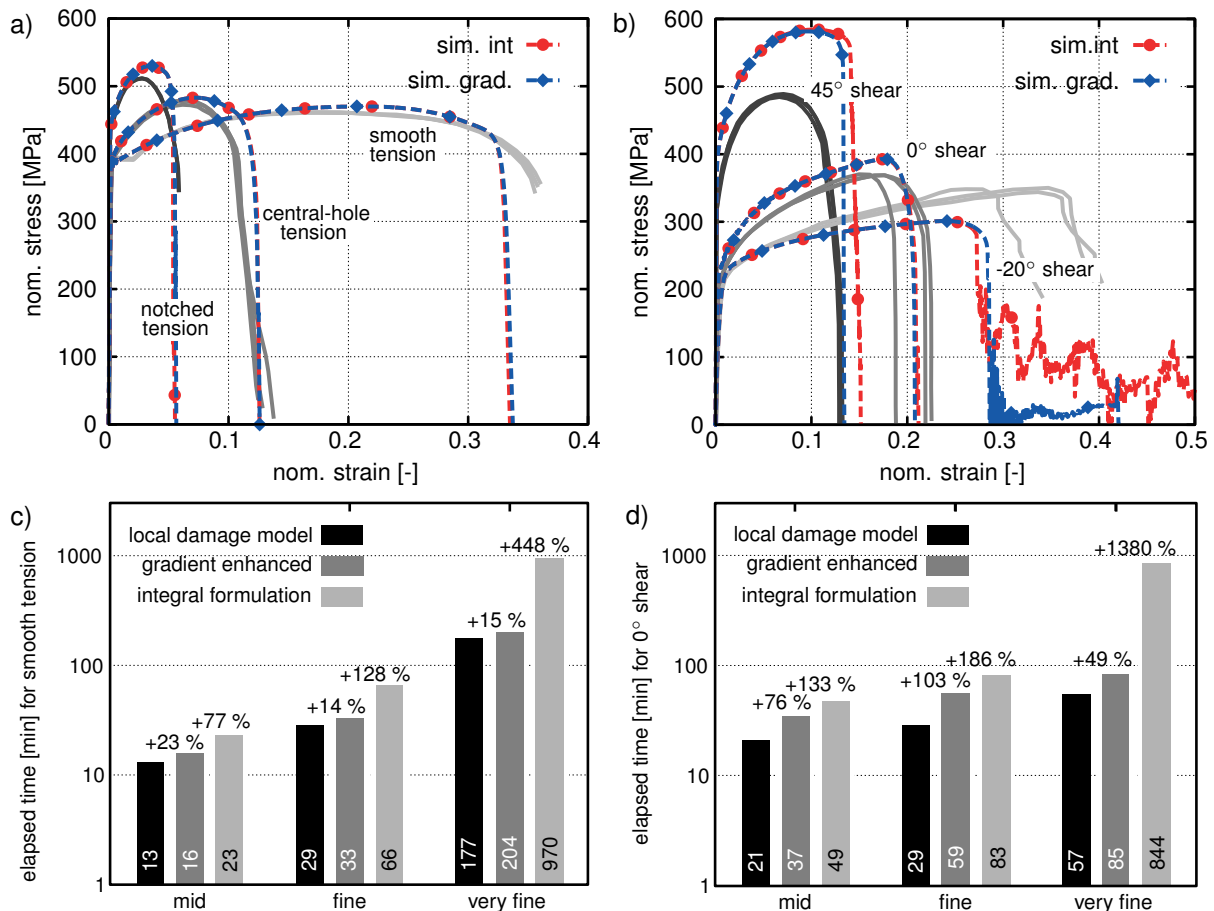

**Abb. 1:** Simulation results (dashed lines) compared to test data from [6] (solid lines) for tensile specimens in a) and shear specimens in b) as well as elapsed simulation time for the smooth tension specimen in c) and the 0° shear specimen in d) with three different mesh sizes (mid: 0.5 mm, fine: 0.25 mm, very fine: 0.125 mm)

**Danksagung** Open access funding enabled and organized by Projekt DEAL.

## Literatur

- [1] M. Nahrman and A. Matzenmiller, Modelling stress-state dependent nonlocal damage and failure of ductile metals, *Proc Appl Math Mech* **20**, e202000054 (2021).
- [2] M. Nahrman and A. Matzenmiller, Modelling of nonlocal damage and failure in ductile steel sheets under multiaxial loading, in review of *Int J Solids Struct* (2021).
- [3] D. Mohr and S. J. Marcadet, Micromechanically-motivated phenomenological Hosford-Coulomb model for predicting ductile fracture initiation at low stress triaxialities, *Int J Solids Struct* **67-68**, 40–55 (2015).
- [4] G. Pijaudier-Cabot and Z. P. Bažant, Nonlocal Damage Theory, *J Eng Mech* **113**, 1512–1533 (1987).
- [5] R.H.J. Peerlings, R. de Borst, W.A.M. Brekelsmann and J.H.P. de Vree, Gradient enhanced damage for quasi-brittle materials, *Int J Numer Methods Eng* **39**, 3391–3403 (1996).

- [6] A. Trondl, S. Klitschke, W. Böhme and D.-Z. Sun, Verformungs- und Versagensverhalten von Stählen für den Automobilbau unter crashartiger mehrachsiger Belastung, FAT-Schriftenreihe 283, Forschungsvereinigung Automobiltechnik e.V. (2016).